

## Mechanism of the anomalous temperature dependence of coercivity in $\text{Sm}(\text{Co}, \text{Fe}, \text{Cu}, \text{Zr})_z$ high-temperature magnets

Chuan-bing Rong<sup>a)</sup>

State Key Laboratory of Magnetism, Institute of Physics and Center for Condensed Matter Physics, Chinese Academy of Sciences, Beijing 100080, China and Department of Physics, University of Texas at Arlington, Arlington, Texas 76019

Hong-wei Zhang and Bao-gen Shen

State Key Laboratory of Magnetism, Institute of Physics and Center for Condensed Matter Physics, Chinese Academy of Sciences, Beijing 100080, China

J. Ping Liu

Department of Physics, University of Texas at Arlington, Arlington, Texas 76019

(Received 19 September 2005; accepted 18 December 2005; published online 24 January 2006)

Coercivity mechanism of the precipitation-hardened  $\text{Sm}(\text{Co}, \text{Fe}, \text{Cu}, \text{Zr})_z$  high-temperature magnets was found to vary with temperature by measurements of reversible magnetization. The magnetization reversal is mainly controlled by domain-wall pinning when temperature is lower than 800 K, while is mainly dominated by nucleation at higher temperature. It is interesting to find that the anomalous temperature dependence of coercivity  $H_c(T)$  near Curie temperature of the 1:5 phase is caused by the fast drop of intergranular exchange coupling. This mechanism can also explain the coercivity behavior that the anomalous  $H_c(T)$  tends to disappear with increasing  $z$  value. © 2006 American Institute of Physics. [DOI: 10.1063/1.2167795]

Recently, the SmCo-based permanent magnets have attracted considerable attention due to the need for developing magnets for high-temperature applications. Moreover, the anomalous temperature dependence of the coercivity  $H_c(T)$ , i.e., a positive temperature coefficient in a certain temperature range, is found in the precipitation-hardened  $\text{Sm}(\text{Co}, \text{Cu}, \text{Fe}, \text{Zr})_z$  magnets.<sup>1–7</sup> The high coercivity in these magnets originates from a complex microstructure consisting of a superposition of cellular and a lamellar structure.<sup>8–10</sup> Although much effort has been paid to understand the anomalous coercivity, up until now the mechanism of the anomalous  $H_c(T)$  in  $\text{Sm}(\text{Co}, \text{Cu}, \text{Fe}, \text{Zr})_z$  magnets is still the subject of debate. The major proposal is domain-wall pinning mechanism which suggests that  $H_c$  should be proportional to the difference of the domain-wall energy density between the 2:17 and 1:5 phases.<sup>2–4,11</sup> Another point is that the anomalous  $H_c(T)$  is caused by a temperature-induced transition from a repulsive to an attractive pinning of domain wall and then to the nucleation of reversed domain at the temperature higher than Curie temperature of 1:5 phase ( $T_c^{1:5}$ ).<sup>1,12</sup> Due to the difficulty in explaining the dependence of coercivity on the Cu content, Gabay *et al.*<sup>5,6</sup> suggested that  $H_c(T)$  is exclusively controlled by the nucleation of reversed domain. However, there still are some unclear coercivity behavior in these precipitation-hardened  $\text{Sm}(\text{Co}, \text{Cu}, \text{Fe}, \text{Zr})_z$  magnets using the above models. For example, the tendency for the anomalous  $H_c(T)$  decreases with increasing  $z$  value.

In this work, measurements of reversible and irreversible magnetization have been used to examine the coercivity mechanism of the  $\text{Sm}(\text{Co}, \text{Cu}, \text{Fe}, \text{Zr})_z$  magnets magnets at different temperature. It is interesting to find that the coercivity mechanism varies with temperature. Being different from point of views of domain-wall pinning and nucleation

mechanisms, we found that the anomalous  $H_c(T)$  is caused by the fast drop of exchange coupling interaction near the temperature of  $T_c^{1:5}$ .

Ingots with nominal composition  $\text{Sm}(\text{Co}_{\text{bal}}\text{Cu}_{0.1}\text{Fe}_{0.1}\text{Zr}_{0.03})_z$  with  $z=6.5, 7.0$ , and  $7.5$  were prepared by arc-melting technique. The ribbons were obtained using the melt-spinning technique with the surface speeds of the Cu wheel about 15 m/s. Subsequently, the samples were isothermally annealed at 1123 K for 3 h, followed by a slow cooling (rate of 1 K/min) to 673 K and then quenched to room temperature (RT). Crystalline structure was determined by x-ray diffraction (XRD) with Cu  $K\alpha$  radiation. XRD analysis shows that all the ribbons are isotropic. A single  $\text{TbCu}_7$ -type phase is obtained in the as-spun ribbons and is further segregated into 1:5 and 2:17 phases after precipitation hardening. The magnetic measurements were performed in a superconducting quantum interference device magnetometer and a Lakeshore vibrating sample magnetometer with maximum applied field of 5 and 2.4 T, respectively. The Curie temperatures of 1:5 and 2:17 phases ( $T_c^{1:5}$  and  $T_c^{2:17}$ ) are obtained from the measured thermomagnetic curves. The determined  $T_c^{1:5}$  of the samples with  $z=6.5–7.5$  are 940, 900, and 870 K, respectively.  $T_c^{2:17}$  is fixed at 1120 K for different  $z$  value.

Figure 1 shows the  $H_c(T)$  curves of the  $\text{Sm}(\text{Co}, \text{Cu}, \text{Fe}, \text{Zr})_z$  magnets. It shows an maximum at temperature  $T_{\text{max}}=800$  K for the sample with  $z=6.5$ . This anomaly of coercivity disappears in the samples with  $z=7.0$  and  $7.5$ . It is interesting to note that although the shape of  $H_c(T)$  curve varies with the increase of  $z$  value, the coercivity almost converges at the same values above 800 K. According to either pinning or nucleation mechanism,<sup>5,11</sup>  $T_{\text{max}}$  should be equal to  $T_c^{1:5}$ . To study the relation between them,  $T_c^{1:5}$  of the sample with  $z=6.5$  is indicated by arrows in Fig. 1. As can be seen clearly that  $T_{\text{max}}$  is far lower than  $T_c^{1:5}$ .

<sup>a)</sup>Electronic mail: crong@uta.edu

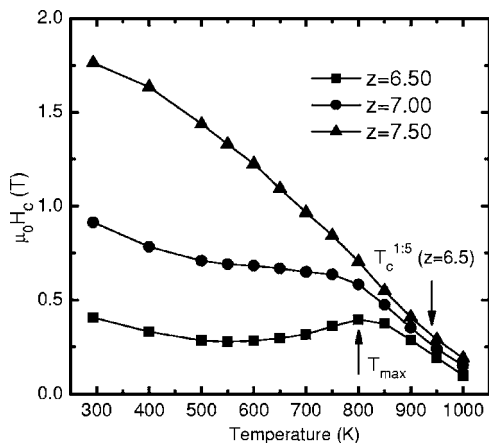


FIG. 1.  $H_c(T)$  curves of the precipitation-hardened  $\text{Sm}(\text{Co,Fe,Cu,Zr})_z$  magnets.

Earlier studies showed that the Cu content in the center of cell boundary is far higher than that of the 1:5/2:17 interface in the precipitation-hardened magnets.<sup>3</sup> This should lead to the wide distribution of  $T_c^{1:5}$  because it depends sensitively on the Cu content.<sup>13</sup> Thus,  $T_{\text{max}}$  may be strongly related to  $T_c^{1:5}$  of the center of the cell boundary, which is smaller than the  $T_c^{1:5}$  determined by the thermomagnetic analysis. This cause the large difference between  $T_{\text{max}}$  and  $T_c^{1:5}$ .

It was proposed by Crew *et al.*<sup>14,15</sup> that the measurements of reversible magnetization  $J_{\text{rev}}$  and its dependence on irreversible magnetization  $J_{\text{irr}}$  could be used to distinguish the magnetization reversal of domain-wall pinning and nucleation of reversed domain. Figure 2 shows the reduced reversible magnetization  $m_{\text{rev}} (=J_{\text{rev}}/J_r)$  versus reduced irreversible magnetization  $m_{\text{irr}} (=J_{\text{irr}}/J_r)$  of the  $\text{Sm}(\text{Co,Fe,Cu,Zr})_{6.5}$  magnet at different temperatures. The curves display a behavior characteristic of domain wall pinning at temperature below 800 K. At low field,  $m_{\text{rev}}$ , which is proportional to the amount of domain-wall bowing, increases due to the fast increases of the domain walls nucleate and the domain-wall area. After a certain stage in reversal, the total area of domain walls reaches a maximum and  $m_{\text{rev}}$  decreases as reversal proceeds further. Thus, the  $m_{\text{rev}}$  versus  $m_{\text{irr}}$  curves exhibit a minimum and are very similar to the results of Crew *et al.*<sup>14</sup> The pinning coercivity mechanism at RT is also proven by the angular dependence of coercivity of other recent works.<sup>16,17</sup> It is interesting to note that the value of the

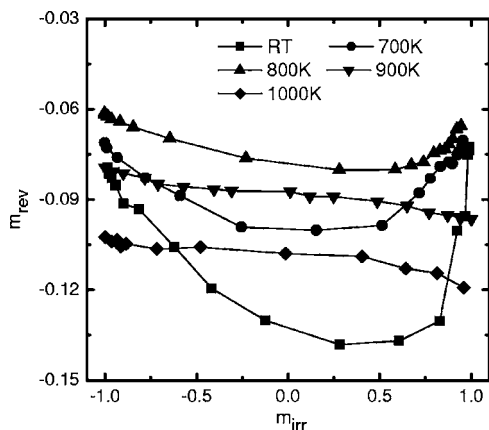


FIG. 2.  $m_{\text{rev}}$  vs  $m_{\text{irr}}$  of the  $\text{Sm}(\text{Co,Fe,Cu,Zr})_{6.5}$  magnets at different temperatures.

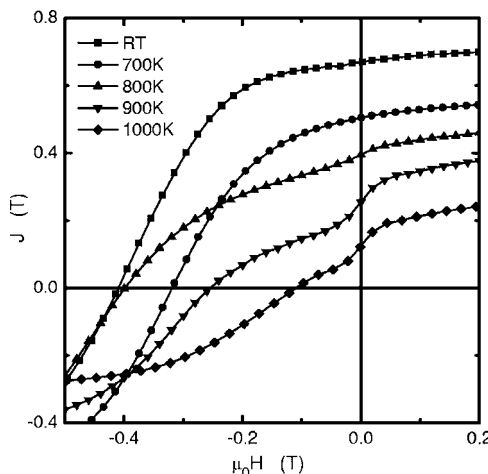


FIG. 3. The demagnetization curves of the  $\text{Sm}(\text{Co,Fe,Cu,Zr})_{6.5}$  magnet at different temperatures.

minimum  $m_{\text{rev}}$  decreases with the increase in temperature. This means that the pinning field in the  $\text{Sm}(\text{Co,Cu,Fe,Zr})_z$  magnets weakens with elevating temperature. By further increasing the temperature above 800 K,  $m_{\text{rev}}$  decreases linearly with increasing  $m_{\text{irr}}$ . This suggests that the reversal mechanism at high temperature is primarily associated with nucleation, and domain walls play a small part in the reversible magnetization component. The transition of coercivity mechanism from domain-wall pinning to reversed-domain nucleation supports the the angular coercivity analysis reported in Ref. 16.

Although the anomalous  $H_c(T)$  can be explained by the gradual change of the magnetization reversal mechanism from pinning to nucleation, the reason why the anomalous  $H_c(T)$  disappears by increasing the  $z$  value is still unclear.

Figure 3 shows the demagnetization curves of the  $\text{Sm}(\text{Co,Fe,Cu,Zr})_{6.5}$  sample at different temperatures. The demagnetization curves show a good single-phase magnetic behavior at  $T < 800$  K. However, an two-step demagnetization behavior appears on the demagnetization curves at  $T \geq 800$  K. Since the exchange constant of 1:5 phase drops quickly as the temperature approaches  $T_c^{1:5}$ , the intergranular exchange coupling (IGEC) between the 1:5 and 2:17 phases decreases quickly, as well. This is proven by the  $\delta m(H)$  plots of the  $\text{Sm}(\text{Co,Fe,Cu,Zr})_{6.5}$  sample at different temperatures as given in Fig. 4. It can be seen that the maximum positive  $\delta m$  values decrease with increasing temperatures, which means the fast drop of IGEC in the magnets.<sup>18</sup> When temperature is above 900 K, IGEC is very low. As a result, the 1:5 phase can not be exchange hardened completely by the 2:17 cellular phase at high temperature. This is the reason for the appearance of turning point on the demagnetization curves.

Since  $\text{Sm}(\text{Co,Fe,Cu,Zr})_z$  magnets have a special cellular microstructure, i.e., the 2:17 cells are surrounded by the 1:5 cell boundary, the coercivity of the  $\text{Sm}(\text{Co,Fe,Cu,Zr})_z$  magnets can be described by the theory of single-phase permanent magnets if the 1:5 cell boundary phase is considered as the defects of the 2:17 matrix phase. That is to say, the coercivity of  $\text{Sm}(\text{Co,Fe,Cu,Zr})_z$  magnets can also be described by a phenomenological expression<sup>19,20</sup>

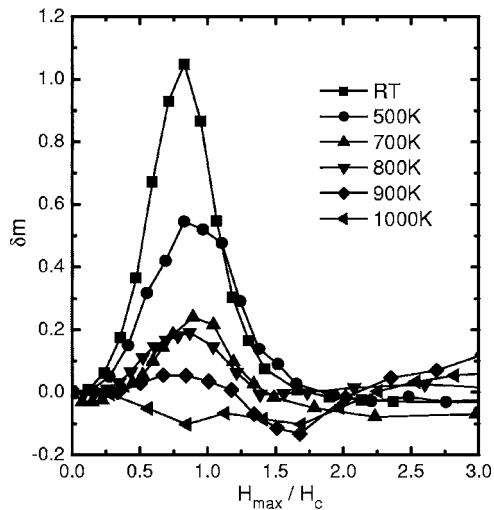


FIG. 4.  $\delta m(H)$  of the  $\text{Sm}(\text{Co,Fe,Cu,Zr})_{6.5}$  magnet at different temperatures.

$$\mu_0 H_c = \alpha_{\text{ex}} \alpha_k \mu_0 H_a - N_{\text{eff}} J_s, \quad (1)$$

where  $\alpha_k$  is the real-structure-dependent Kronmuller parameter and  $N_{\text{eff}}$  is a magnetostatic interaction parameter.  $\alpha_{\text{ex}}$  describes the deleterious effect of exchange coupling between neighboring grains on the coercivity. In general,  $\alpha_{\text{ex}}$  is equal to 1.0 for the exchange decoupled magnets, while it decreases with the increase in IGEC. For  $\text{Sm}(\text{Co,Fe,Cu,Zr})_z$  magnets,  $\alpha_k$  depends only weakly on temperature since the cellular microstructure of the precipitation-hardened magnets does not change with temperature. On the contrary,  $\alpha_{\text{ex}}$  is very low at RT due to the strong IGEC as proven in Fig. 4 and is approximately equal to 1.0 above  $T_c^{1:5}$  since the 2:17 cells are completely isolated by the 1:5 boundaries. Combined with the monotonous decrease of anisotropy field, the temperature dependence of coercivity is the competitive result of the temperature dependences of microstructure parameter  $\alpha_{\text{ex}}(T)$  and anisotropy field  $H_a(T)$ . To investigate the influence of temperature on  $\alpha_{\text{ex}}(T)$  quantitatively, Fig. 5 gives the temperature dependence of remanence ratio  $m_r (=J_r/J_s)$  of the  $\text{Sm}(\text{Co,Fe,Cu,Zr})_z$  magnets. Generally, the

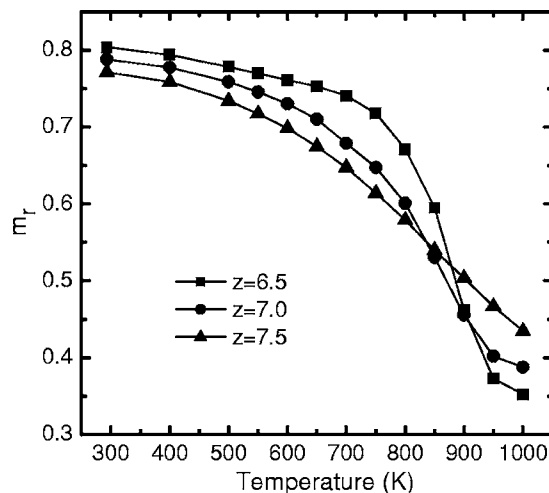


FIG. 5. The temperature dependence of  $m_r$  of the  $\text{Sm}(\text{Co,Fe,Cu,Zr})_z$  magnets.

larger  $m_r$  means the stronger IGEC in a material. As shown in Fig. 5,  $m_r$  is far larger than the Stoner–Wohlfarth theoretical value of one-half at low temperature,<sup>21</sup> while decreases dramatically near  $T_c^{1:5}$  in all samples. This proves that IGEC decreases quickly at temperatures near  $T_c^{1:5}$ . Thus,  $\alpha_{\text{ex}}$  increases fast due to the sharp drop of IGEC. If the magnitude of the increase in  $\alpha_{\text{ex}}(T)$  is faster than of the decrease in  $H_a(T)$ , the anomalous  $H_c(T)$  may be obtained. Furthermore, according to the  $m_r \sim T$  relations presented in Fig. 5,  $\alpha_{\text{ex}}$  increases slower for the sample with larger  $z$  value. This is the reason that the anomalous  $H_c(T)$  tends to disappear with increasing  $z$  value.

In summary, the coercivity mechanism of the precipitation-hardened  $\text{Sm}(\text{Co,Fe,Cu,Zr})_z$  magnets has been found to vary with temperature. The magnetization reversal is mainly controlled by domain-wall pinning when  $T \leq 800$  K, while the reversal is mainly dominated by nucleation at  $T > 800$  K. It is interesting to find that  $H_c(T)$  of the precipitation-hardened magnets is the competitive result of the temperature dependences of IGEC and anisotropy field. The fast drop of IGEC at the temperature near  $T_c^{1:5}$  leads to the fast increase of  $\alpha_{\text{ex}}$  and the anomalous  $H_c(T)$ . Since  $\alpha_{\text{ex}}$  increases slower for the sample with larger  $z$  value, the anomalous  $H_c(T)$  tends to disappear with increasing  $z$  value.

The work was supported by the National Science Foundation of China and the U.S. DoD/MURI under the Grant No. N00014-05-1-0497.

- <sup>1</sup>A. G. Popov, A. V. Korolev, and N. N. Shchegoleva, *Phys. Met. Metallogr.* **69**, 100 (1990).
- <sup>2</sup>J. F. Liu, T. Chui, D. Dimitrov, and G. C. Hadjipanayis, *Appl. Phys. Lett.* **73**, 3007 (1998).
- <sup>3</sup>D. Goll, I. Kleinschroth, W. Sigle, and H. Kronmuller, *Appl. Phys. Lett.* **76**, 1054 (2000).
- <sup>4</sup>J. Zhou, R. Skomski, C. Chen, G. C. Hadjipanayis, and D. J. Sellmyer, *Appl. Phys. Lett.* **77**, 1514 (2000).
- <sup>5</sup>A. M. Gabay, W. Tang, Y. Zhang, and G. C. Hadjipanayis, *Appl. Phys. Lett.* **78**, 1595 (2001).
- <sup>6</sup>J. Zhang, H. Liu, C. B. Rong, H. W. Zhang, S. Y. Zhang, B. G. Shen, Y. Q. Bai, and B. H. Li, *Appl. Phys. Lett.* **83**, 1172 (2003).
- <sup>7</sup>C. B. Rong, J. Zhang, H. W. Zhang, X. B. Du, S. Y. Zhang, and B. G. Shen, *J. Magn. Magn. Mater.* **279**, 143 (2004).
- <sup>8</sup>G. C. Hadjipanayis, E. J. Yadlowsky, and S. H. Wollins, *J. Appl. Phys.* **53**, 2386 (1982).
- <sup>9</sup>J. Fidler and P. Skalicky, *J. Magn. Magn. Mater.* **27**, 127 (1982).
- <sup>10</sup>C. B. Rong, H. W. Zhang, J. Zhang, X. B. Du, S. Y. Zhang, and B. G. Shen, *J. Appl. Phys.* **97**, 33907 (2005).
- <sup>11</sup>J. D. Livingston and D. L. Martin, *J. Appl. Phys.* **48**, 1350 (1977).
- <sup>12</sup>D. Goll, H. Kronmuller, and H. H. Stadelmaier, *J. Appl. Phys.* **96**, 6534 (2004).
- <sup>13</sup>E. Lectard, C. H. Allibert, and R. Ballou, *J. Appl. Phys.* **75**, 6277 (1994).
- <sup>14</sup>D. C. Crew, R. C. Woodward, and R. Street, *J. Appl. Phys.* **85**, 5675 (1999).
- <sup>15</sup>D. C. Crew, P. G. McCormick, and R. Street, *J. Appl. Phys.* **86**, 3278 (1999).
- <sup>16</sup>I. Panagiotopoulos, M. Gjoka, and D. Niarchos, *J. Magn. Magn. Mater.* **279**, 389 (2004).
- <sup>17</sup>C. B. Rong, H. W. Zhang, S. L. He, R. J. Chen, and B. G. Shen, *Appl. Phys. Lett.* **86**, 122506 (2005).
- <sup>18</sup>P. E. Kelly, K. O. Grady, P. I. Mayo, and R. W. Chantrell, *IEEE Trans. Magn.* **25**, 3881 (1989).
- <sup>19</sup>D. Goll, M. Seeger, and H. Kronmuller, *J. Magn. Magn. Mater.* **185**, 49 (1998).
- <sup>20</sup>R. Skomski, *J. Phys.: Condens. Matter* **15**, R841 (2003).
- <sup>21</sup>E. C. Stoner and E. P. Wohlfarth, *Philos. Trans. R. Soc. London* **240**, 599 (1948).